

REPORT

issued by an Accredited Testing Laboratory

Contact person RISE
Thomas Vaessen
Materials and Production
+46 10 516 51 79
thomas.vaessen@ri.se

Date 2020-09-14

Reference 2F020149-01

Page 1 (6)

Ovacon AB Dahn Ahlström Box 64 61922 Trosa Sweden

Emission measurements according to M1

(3 appendices)

Assignment

Emission measurement according to "M1 Emission Classification of Building Materials: Protocol for Chemical and Sensory Testing of Building Materials", ver 15.11.2017, after 28 days of conditioning regarding volatile organic compounds, carcinogenic compounds (EU Regulation No 1272/2008 Annex VI, cat 1A and 1B), formaldehyde, ammonia and sensory acceptability.

Product/test specimen

Table 1.

	·
Product type:	Glass fibre insulation
Product name:	Spraytec G
Batch No:	See Sampling report
Manufacturing date:	2020-07-02
Packaging:	Wrapped in aluminium foil and plastic
Arrived at RISE:	2020-07-09
Test specimen preparation:	Floor scenario is used for the testing.
	The sample preparation was made by the customer, see Sampling report. The glass fibre insulation was applied on a stainless steel plate of 0.80 x 0.80 m and one plate of 0.45 x 0.45 m. Chemical testing: the 0.45 x 0.45 plate was used with a surface area of 0.2 m ² . Sensory testing: the 0.8 x 0.8 plate was used with a surface area of 0.65 m ² .
Deviation from protocol:	-
Test period started, date:	2020-07-15
Conditions during ageing:	23 ± 2 °C, 50 ± 5 % RH
Emission samplings, date:	2020-08-13





Methods

The specimens were conditioned outside the testing chambers in separate conditioning containers (with air velocity of ca 0.2 m/s) in a room with controlled climate conditions of 23 ± 2 °C and 50 ± 5 % RH. The specimens were placed in the chambers three days before the measurements of the chemical emission and two days before the sensory evaluation.

Table 2. Chamber conditions of the test of chemical emissions

Test chamber volume:	0.25 m ³ , stainless steel
Temperature:	23 ± 1 °C
Relative Humidity:	50 ± 3 % RH
Air exchange rate:	0.5 h ⁻¹
Air velocity at specimen surface:	0.1 - 0.3 m/s
Area of sample:	$0.2m^2$
Area specific air flow rate:	$0.6 \text{ m}^3/\text{m}^2\text{h}$

Table 3. Chamber conditions of the test of sensory acceptability

Test chamber volume:	1.0 m ³ , stainless steel
Temperature:	23 ± 1 °C
Relative Humidity:	50 ± 3 % RH
Supply air flow rate:	$0.9 \text{ l/s} = 3.2 \text{ m}^3/\text{h}$
Area of sample:	0.65 m ²

Table 4. Emission sampling and analytical methods

Test	Sampling method	Adsorbent	Sampling volume (litre)	Analysis method / Quantification	Detection limit
VOC	ISO 16000-9:2006 ¹	Tenax TA	3 - 6	RISE 0601 ² / FID quantification	$1 \mu g/m^3$
Formaldehyde	ISO 16000-9:2006 ¹	DNPH	33	RISE 2303 ³ /HPLC-UV	0.03 µg/sampler
Ammonia	ISO 16000-9:2006 ¹	Treated silica gel	270 - 330	Liquid chromatograph with conductivity detector ⁴	0.9 µg/sampler
Sensory evaluation	ISO 16000-28:2012 ⁵			Acceptability, Untrained panel of min 15 persons	

¹⁾ In accordance with ISO 16000-9:2006 and M1 protocol.

Tenax TA was used as adsorption medium for VOC The tubes were thermally desorbed and analysed in accordance to RISE method 0601, similar to ISO 16000-6:2011 (Determination of volatile organic compounds in indoor and test chamber air by active sampling on Tenax TA sorbent, thermal desorption and gas chromatography using MS/FID). This means an analysis in a gas chromatograph and detection with a flame ionisation detector (FID) and mass selective detector (MS). The FID signals are used for compound quantification. The TVOC is quantified as toluene equivalents. The mass selective detector is used for identification of compounds.

²⁾ In accordance with ISO 16000-6:2011 and M1 protocol.

³⁾ In accordance with ISO 16000-3:2001.

⁴⁾ Not accredited method.

⁵⁾ In accordance with M1 protocol, not accredited method.



The capillary column used is coated with 5% phenyl/95 % methylpolysiloxane. Tenax TA was also used as adsorption medium for testing of volatile carcinogenic compounds, according to EU Regulation No 1272/2008 Annex VI, cat 1A and 1B), (exclusive formaldehyde), 0.001 mg/m³ and above.

The sampling of formaldehyde was carried out with DNPH samplers. The samplers were analysed according to RISE method 2302, similar to ISO 16000-3:2011(Indoor air--Part 3: Determination of formaldehyde and other carbonyl compounds – Active sampling method), which means analysis on a liquid chromatograph with absorbance detector.

The sampling of ammonium was carried out with silicagel treated adsorbent tubes and analysis on a liquid chromatograph with conductivity detector.

Minimum two subsequent samples were taken for the VOC determination, for the formaldehyde and for the ammonia respectively.

Results

The results relate only to the items tested. Decision rule: When comparing the measured results and requirement level, the average value of the measured results has been compared with the requirement level. No account is taken to the measurement uncertainty.

The results of the chemical testing are expressed as area specific emission rates and as concentrations in a model room. The model room has a base area of 3 m x 4 m and a height of 2.5 m, with an air exchange rate of 0.5 h^{-1} . The wall area is 31.4 m^2 , floor area is 12 m^2 , small area, like a door, is 1.6 m^2 and very small area, like sealant, is 0.2 m^2 . Floor area is used for the calculation of the concentrations.

Calculation of the concentration from the emission rate:

$$Conc = \frac{SER_A \times A}{n \times V}$$

$$Conc = concentration of a VOC in the model room, in $\mu g/m^3$

$$SER_a = area \text{ specific emission rate, in } \mu g/m^3$$

$$A = area \text{ of sample, in } m^2$$

$$n = air \text{ exchange rate, in changes per hour}$$

$$V = \text{ volume of the model room, in } m^3$$$$

Table 5. Results of the chemical testing of the sample **Spraytec G** after 28 days

Compound	Concentration in model room mg/m ³	Emission rate mg/m²h	Criteria M1 mg/m²h
TVOC ⁶	< 0.01	< 0.01	< 0.2
Carcinogens	< 0.001	< 0.001	< 0.001
Single VOC (µg/m ³)	≤ EU-LCI	-	≤ EU-LCI
Formaldehyde	< 0.005	0.003	< 0.05
Ammonia ⁷	< 0.005	0.002	< 0.03

⁶⁾ The TVOC is the sum of the individual concentration $> 5 \mu g/m^3$ in model room.

⁷⁾ Not accredited method.

2F020149-01

Table 6.Results of the sensory acceptability evaluation of the sample **Spraytec G**, after 28 days

Evaluator	Sensory evaluation	Criteria M1
1	0.94	
2	0.96	
3	0.06	
4	0.92	
5	0.92	
6	0.86	
7	0.96	
8	0.7	
9	0.9	
10	0.96	
11	0.96	
12	0.9	
13	0.9	
14	0.8	
15	0.6	
Arithmetic mean of acceptability ⁸	0.82	≥+0.0
Standard deviation	0.24	
90 % confidence interval of arithmetic mean	0.1	≤ 0.2

⁸⁾ Not accredited method.

The empty sensory test chamber acceptability was determined 2020-08-13. The mean acceptability vote of the empty chamber was ≥ 0.8 .

Interpretation of the results

The tested product $\mbox{\bf Spraytec }\mbox{\bf G}$ complies with all the requirements of M1 for the tested parameters.

Detailed results

Table 7. Detailed results (emission rates) of the chemical testing after 28 days

Sample	TVOC (mg/m^2h) as toluene equivalents between C_6 - C_{16}	Formaldehyde (mg/m²h)	Ammonia (mg/m²h)	Carcinogens (mg/m²h) between C ₆ -C ₁₆
1	< 0.01	0.005	0.002	< 0.001
2	0.01	< 0.002	0.002	< 0.001



Table 8. Single VOCs above $5 \mu g/m^3$ in the model room

Single VOCs	CAS number	Retention time (min)	ID 9	Emission rate (µg/m²h)	Concentration (µg/m³)
Single VOCs C ₆ -C ₁₆ :		6.9 - 39			
Toluene	108-88-3	11.1	A	8	6
TVOC		6.5 - 38	A		
Volatile Carcinogens 10		6.9 - 39			
No substances detected			В	< 1	< 1
Single VOC outside C ₆ – C ₁₆ :					
VVOC $(< C_6)^{11}$		5.3 - 6.9			
No single VVOC detected			В	< 2	< 5
SVOC (C ₁₆ – C ₂₂) ¹²		39 - 52			
No single SVOC detected			В	< 2	< 5

⁹⁾ ID: A = quantified compound specific, B = quantified as toluene-equivalent

TVOC is the sum of all individual substances with concentrations $\geq 5~\mu g/m^3$ (in toluene equivalents).

Level of identification of compounds is 100 % for all compounds $\geq 5 \,\mu g/m^3$.

Table 9. Detected EU LCI-compounds $\geq 5 \mu g/m^3$ quantified by compound specific response factor

Single VOCs	CAS number	Retention time (min)	ID 9	Concentration (µg/m³)	EU LCI _i (Dec 2019) (μg/m ³)
Single VOCs C6-C16:		6.9 - 39			
Toluene	108-88-3	11.1	A	6	2900

⁹⁾ ID: A = quantified compound specific, B = quantified as toluene-equivalent

Measurements uncertainty

The expanded measurement uncertainty of VOC result is 15 % (rel) and formaldehyde is 30 % (rel). For ammonia the measurement uncertainty is estimated to 20 % (rel).

See Appendix 1 for a gas chromatogram from the VOC determination and Appendix 2 for a photo of a the test specimen. Appendix 3 is the Sampling report received from the customer.

¹⁰⁾ Volatile carcinogens = VOCs according to EU Regulation No 1272/2008 Annex VI, cat 1A and 1B

¹¹⁾ VVOC = very volatile organic compounds, as defined in ISO 16000-6 (not accredited)

¹²⁾ SVOC = semi-volatile organic compounds, as defined in ISO 16000-6 (not accredited)



RISE Research Institutes of Sweden AB Materials and Production – Chemical and Biological Safety

Performed by Examined by

Thomas Vaessen Eskil Sahlin

Appendices


- 1. Gas Chromatogram
- 2. Photo of the test specimen
- 3. Sampling report



Gas chromatogram

Sample: Spraytec G, after 28 days

Abundance

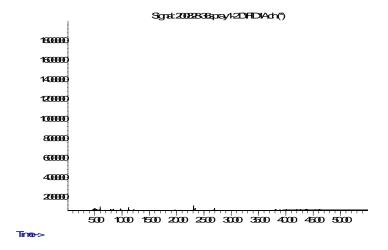

TVOC between C_6 and C_{16} , means compounds eluting between 6.9 and 39 minutes.

RI. SE



Photo of the test specimen





Appendix 3

Sampling Report

Sampler (Name, Company, contact info): Dahn Ahlström	Manufacturer of the product (Company, address): Ovacon AB
Ovacon AB	Bråtagatan 8A
0738-510312	61922 Trosa
	Sverige
Name of product:	Type of product:
SprayTec G	Glasfiberisolering
Manufacturing Date:	Batch No:
2020-07-02	-
Date of sampling:	Amount/size of material sampled:
2020-07-02	600x600x50
	Packing material: aluminiumfolie + plastic
Sample is taken from:	How was the product stored before sampling?
Production line X	Directly from production into packaging
Stock / Storage Miscellaneous	
-where, specify:	
where, speary.	
If a sub-sample was collected from a larger mater	ial amount, describe how the sub-sample was
taken:	
Observations and remarks:	
Confirmation	
I hereby confirm that the sample was selected, taken as	nd packed in accordance with the instructions
Date:	Signature:
2020-09-08	Daha Alles
	NAMOO LOUNCE